


# SEAUPG 2003 CONFERENCE




## Permeability

Allen Cooley


Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants

## Why is Coarse-Graded Superpave More Permeable?

Superpave



Conventional



Equal Air Volumes (% VTM)

- Coarser Gradation  
- Larger Sized Voids  
(more chance for inter-connected voids)
- Denser Gradation  
- Smaller Sized Voids  
(less chance for inter-connected voids)

Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants

## Field Permeameter Device





Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants



## Factors Affecting Permeability in the Field

- Pavement Density
- NMAS
- Gradation Shape
- Lift Thickness
- Construction Equipment?

Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants

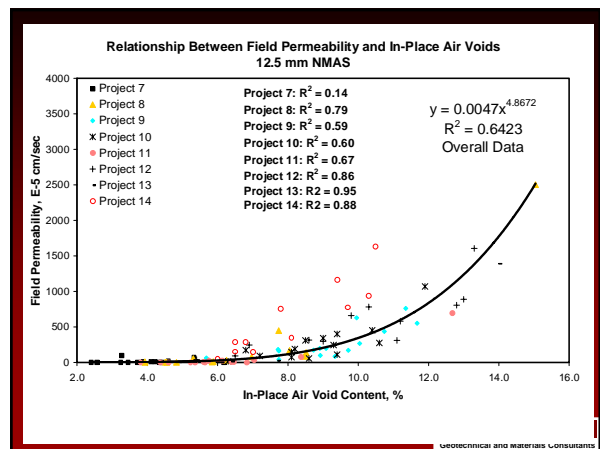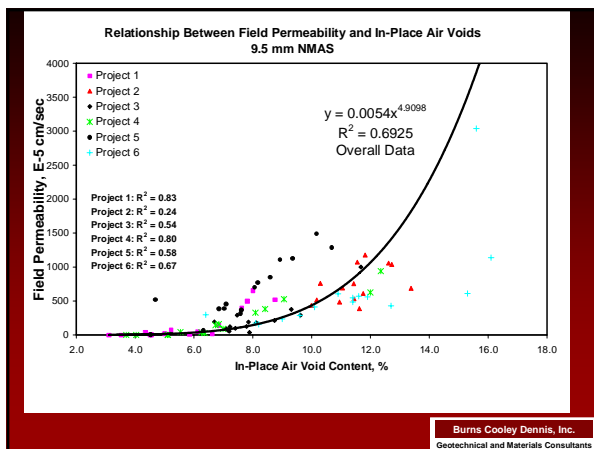


# SEAUPG 2003 CONFERENCE

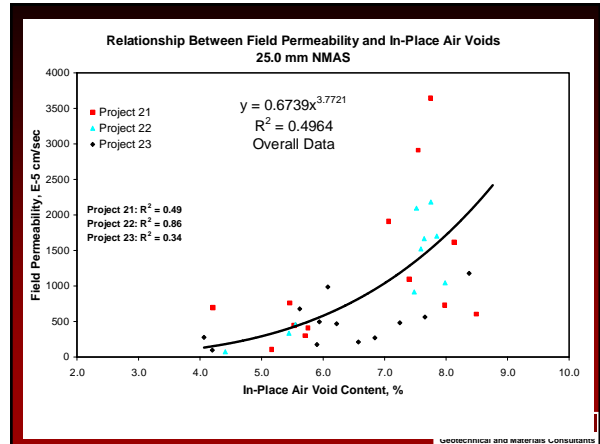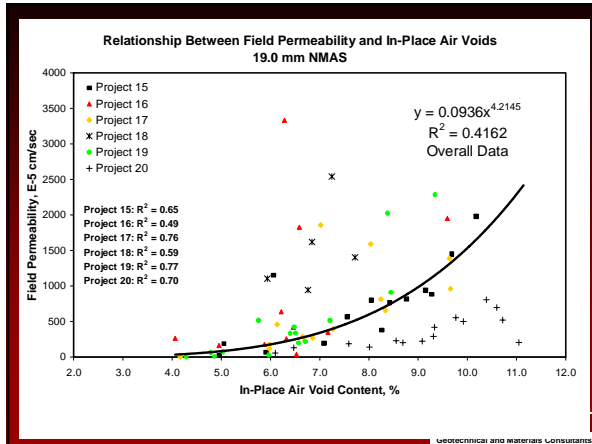

## Critical Density Values

- 9.5 and 12.5 mm NMAS ~ 7.5 – 8.0 %
- 19.0 mm NMAS ~ 6.0 – 6.5 %
- 25.0 mm NMAS ~ 5.5 – 6.0 %

Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants

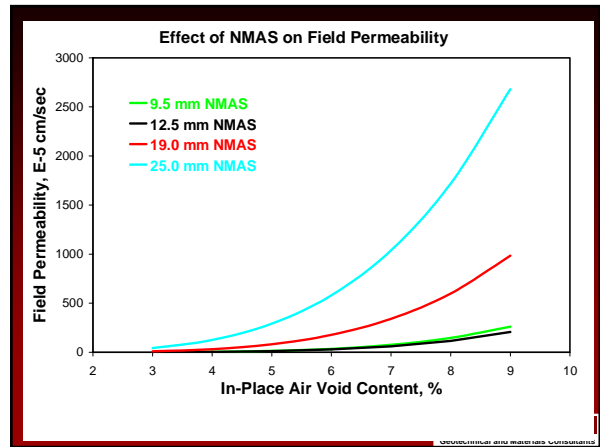

## Effect of Thickness and Equipment

Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants




## Effect of Thickness and Equipment

- Seven Mixes at NCAT Test Track
- Vary Thickness (Crank Screenshot)
- Roller Type
  - Steel Wheel
  - Steel Wheel/Rubber Tire

2:1      5:1

Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants

# SEAUPG 2003 CONFERENCE

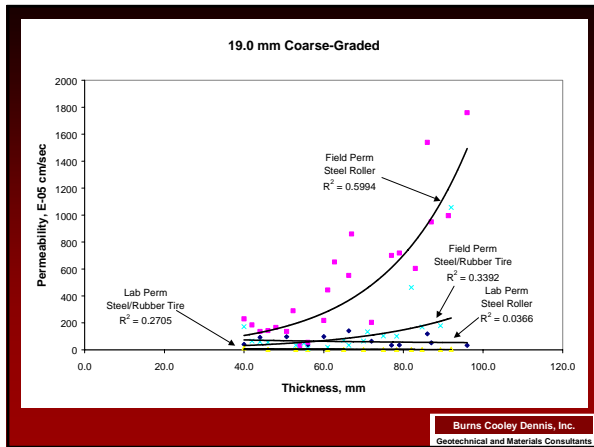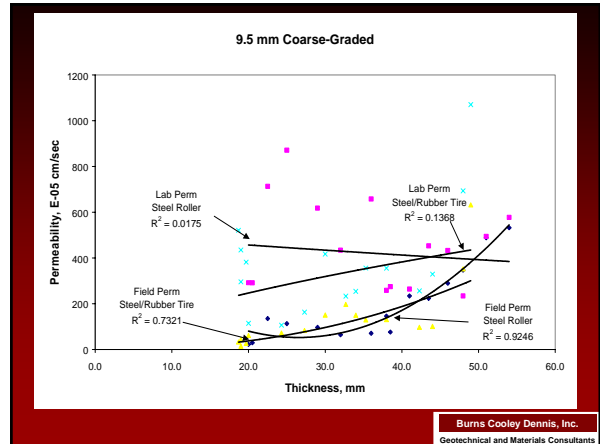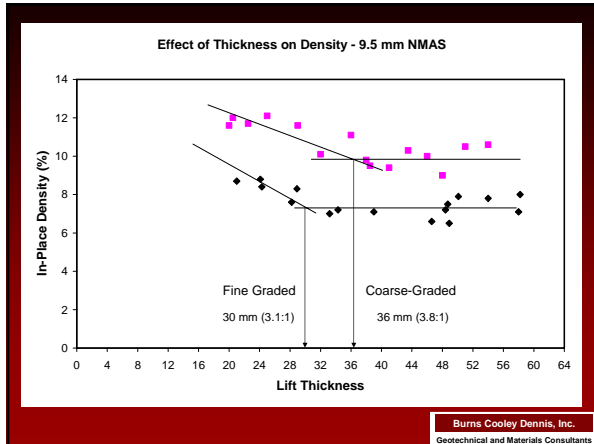

## Is There a Tool to Predict Permeability at Design or QC?


- Water Absorption from T166?
  - Defining permeable voids?
- Lab Permeability during Design

Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants







## Predict Field Problems During Mix Design/QC?

- Relationship Between Field and Lab Permeability Results?
- Relationship Between Lab Permeability of Field and Lab Compacted Samples?
- Relationship Between Water Absorption and Density?
- Relationship Between Water Absorption and Permeability?

Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants

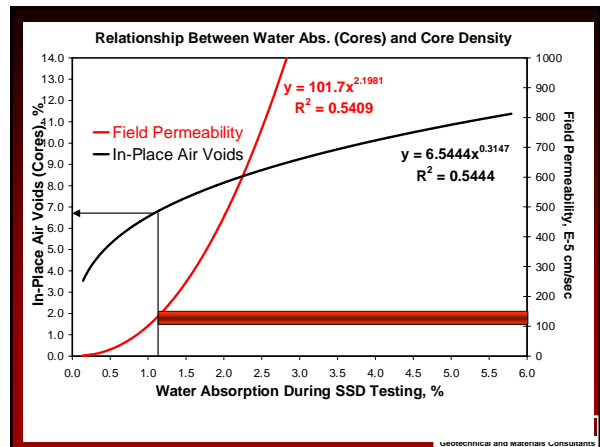

# SEAUPG 2003 CONFERENCE

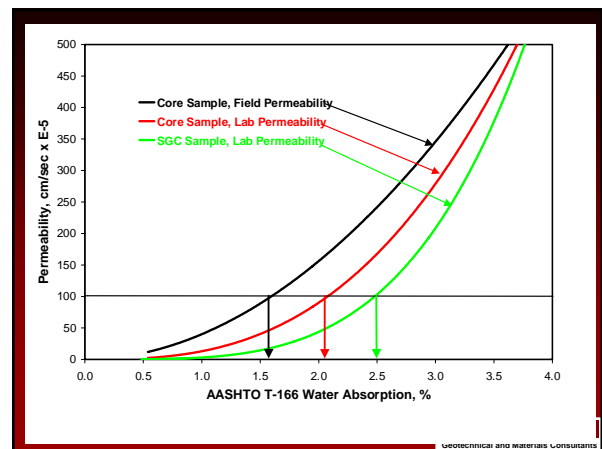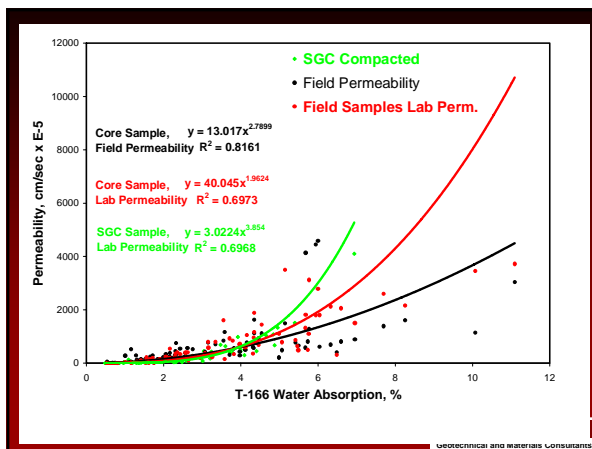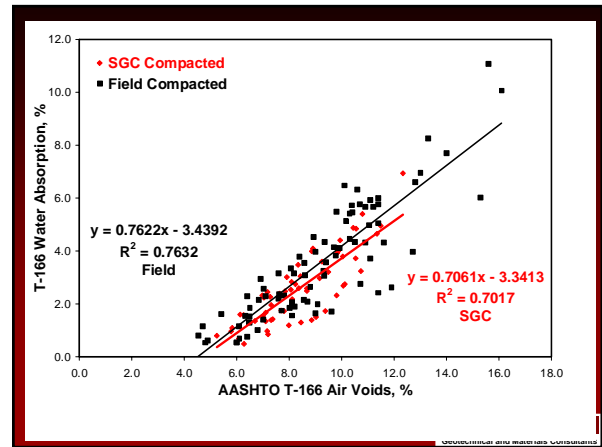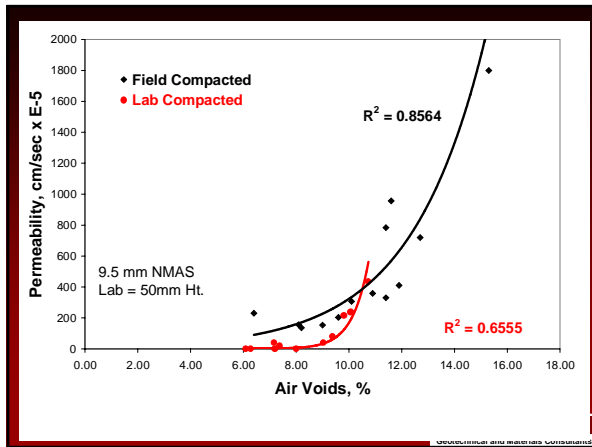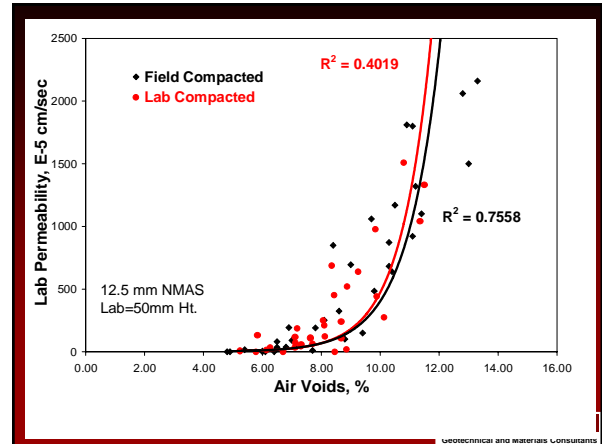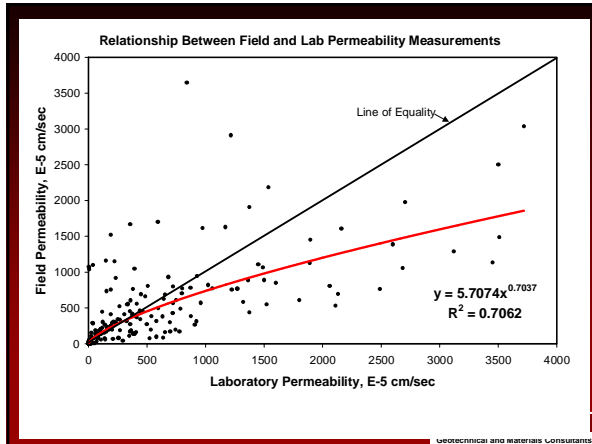

# SEAUPG 2003 CONFERENCE

## Conclusions

- There is a relationship between density and permeability.
- NMAAS and lift thickness affect this relationship.
- Water absorption can be used as a quick check for permeability problems.
- Thickness and Roller type affects permeability

Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants

## Conclusions

- During Mix Design
  - Compact samples to design lift thickness
  - Vary air voids to anticipated field values
  - Determine Lab Permeability and/or Water Absorption
  - If lab permeability above  $125 \times 10^{-5}$  or absorption above  $\approx 2.0\%$ , may have potential permeability problems in the field

Burns Cooley Dennis, Inc.  
Geotechnical and Materials Consultants